

## The Effect of Initial Cooling Temperature on Deformation of U75V Heavy Rail after Cooling

Mingxin Gao<sup>1,a</sup>, Hao Jia<sup>2,b</sup>, Juanjuan Jiang<sup>2,b</sup>, Peilong Wang<sup>2,b</sup>,  
Hua Song<sup>2,b</sup>, Siyu Yuan<sup>3,c</sup> and Zhongqiang Wang<sup>3,c</sup>

<sup>1</sup>Heavy Equipment Manufacturing Factory of China First Heavy Industries, China

<sup>2</sup>University of Science and Technology Liaoning, Anshan, Liaoning 114051, China

<sup>3</sup>Anshan Iron & Steel Co; Ltd., Anshan, Liaoning 114021, China

<sup>a</sup>gaoming31@163.com, <sup>b</sup>songhua88@126.com, <sup>c</sup>wzhq@163.com

**Keywords:** initial temperature, heat-stress couple, cooling bed

**Abstract.** The initial cooling temperature has important effect on the bending change and section size of rolled heavy rail, when rolled heavy rail is on the cooling bed for natural cooling. In the paper, the heat-stress couple method is adopted to carry on numerical simulation to cooling process of 60kg/m U75V heavy rail, and we has obtained the bending change value and section size of rolled heavy rail in different initial cooling temperature. The study is of great reference value on the design of cooling bed which is for hundred-meter high speed heavy rail and the formulation of cooling technological parameters.

### Introduction

When rolled heavy rail is on the cooling bed for natural cooling, its bending deformation caused by solid phase changing and the section size contraction deformation occurs, there are many factors affecting cooling after deformation of heavy rail, such as the initial cooling temperature, environment temperature and cooling rate<sup>[1]</sup>. Reference [1] briefly analyses the impact of the initial temperature on the bending of cold heavy rail, Reference [2,3] study on bending deformation of heavy rail being cooling, and the information that initial cooling temperature effects on rolled heavy rail section size is not reported until now. In the paper, the heat-stress couple method is adopted to carry on numerical simulation to cooling process of 60kg/m U75V heavy rail, and we has obtained the bending change value and section size of rolled heavy rail in different initial cooling temperature. The study is of great reference value on the design of cooling bed which is for hundred-meter high speed heavy rail and the formulation of cooling technological parameters.

### The establishment of heavy rail cooling FEM model

**Establishment of geometric model.** The section shape and size of 60kg/m heavy rail is shown in Figure 1. Considering the complex heavy rail section sizes and the computing time, the fillet of 2mm and 3mm radius have been simplified in this paper, and the model of heavy rail has been taken as length of 2000mm. The SOLID5 unit which has the function of limited coupling between temperature and structure field is adopted in meshing, rail model was classified a total of 44,000 units (dividing 250 equal parts along the length direction), 57,479 node, it is shown in Figure 2.



Table 1 U75 thermal physical parameters

Temperature (°C)	Density $\rho$ (kg/m <sup>3</sup> )	Linear thermal expansion coefficient $\times 10^{-5}$	Elastic modulus $E \times 10^5$ (Mpa)	Poisson ratio $\mu$
30	7760	0.067	2.09	0.3
200	7760	0.179	1.09	0.26
300	7760	0.321		
350	7760		1.89	0.23
400	7760	0.49		
600	7760	0.831	1.68	0.13
700	7760	1.00		
750	7760			
800	7760	1.12		
850	7760		1.329	0.12
900	7760	1.30	1.09	0.12
1000	7760	1.51	0.975	0.12

**Determination of cooling boundary conditions.** To calculate the heat-transfer coefficients during the natural cooling process of heavy rail on the cooling bed, the method of experience formula is adopted in this paper, as follows<sup>[5]</sup>:

$$H = 2.6(T_w - T_c)^{0.25} + 4.84 \times 10^{-8}(T_w^2 + T_c^2)(T_w + T_c) \quad (1)$$

In which:  $T_w$ ——temperature of work piece;  
 $T_c$ ——temperature of environment,  $T_c = 30^\circ\text{C}$ .

### Initial cooling temperature effecting on bending and section sizes of cold heavy rail

Thermo-mechanical coupling module of software Ansys is applied to numerical simulation on 60kg/m U75V heavy rail in the initial temperature respectively of 950°C, 900°C, 870°C and 850°C during the cooling process, and it is found that the bending and the section size change of cooling after heavy rail in different initial cooling temperature.

**Effects of initial cooling temperature on bending.** The simulation result was dealt with by Ansys and Microsoft Excel 2003, it's shown in table 2.

Table 2 The bending curvature radius of cold heavy rail in different initial temperature

Initial temperature	950°C	900°C	870°C	850°C
Curvimeter radius(mm)	1909892	2041941	2256456	2301894

From table 2, the higher initial temperature cooling after rolling is, the smaller bending curvature radius value of cold rail is. In opposition, the lower initial temperature is, the greater bending curvature radius value of cold rail is. In other words, appropriate reducing of initial cooling temperature can reduce the bending of cold rail. The middle line bending curves of cold rail bottom in different initial temperatures are shown in Figure 6.

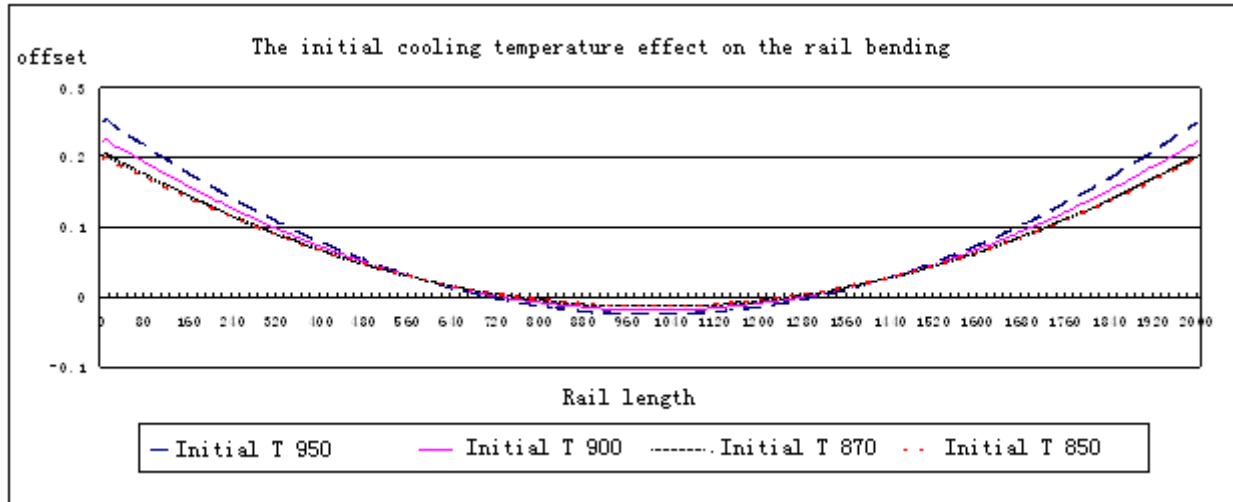


Fig. 6. The relationship of initial cooling temperature and cold rail bending curves

**Effect of initial temperature on the section size.** To study the section size change of cooled rail, the change of rail's dimensions in the height direction( including: height of the rail  $H$ , height of the railhead  $H_1$ , height of the split  $H_2$ , height of the bottom  $H_3$ ) and in the width direction( including: width of the top of railhead  $B_1$ , width of the middle of railhead  $B_2$ , width of the bottom of railhead  $B_3$ , width of the split  $B_4$ , width of the bottom  $B_5$ ) are analyzed, and geometric size measuring points in rail section are shown in Figure 7. Table 3 and table 4 indicates the change of rail dimension in the height and width in different initial temperatures after cooling.

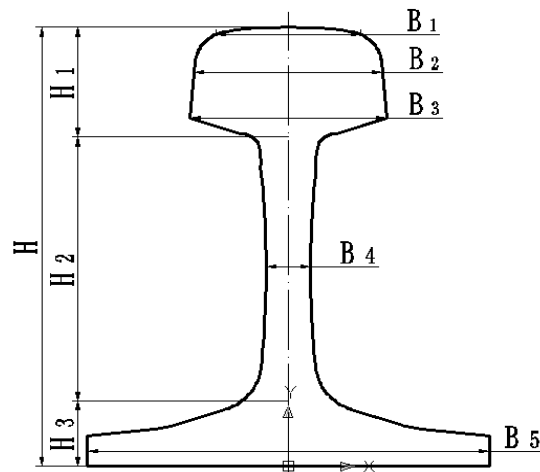


Fig. 7. Measuring points in rail section

As is shown in table 3, after cooling, the height of rail-head's contraction rate is the most, the height of split's the second, the height of bottom's the minimum. As the initial temperature increases before cooling, the contraction and contraction rates of cooled rail along height direction increased with it, but the increment is little. The contraction and contraction rates of rail height, from 850°C, 0.1313mm and 0.7460‰, respectively increase to 950°C, 0.1532mm and 0.8704‰. The contraction increases only 0.0219mm, and contraction rates increases 0.1234 ‰.

From table 4, the cooled rail top width  $B_1$ , the middle width  $B_2$  and the lower part width  $B_3$  contraction rate got the most, and basically the same; it was more than the contraction of rail split width  $B_4$ . The bottom width  $B_5$  has the minimum contraction rate. As the temperature before cooling increased, the contraction and contraction rates increased along rail width direction with it, but the incremental value is little. The  $B_1$  contraction rate along the top width of rail head direction after cooling, from 850°C, 0.774‰ respectively increases to 950°C, 0.907‰, and contraction rate increases 0.123‰.

As is known from table 3 and table 4, in the same initial cooling temperature, the contraction rates of cooled rail in the height and width direction are basically the same, and the contraction deformation of heavy rail is equality.

Table 3 Different initial temperatures cooling after the high rail changes

	Initial temperature	height of rail $H_1$	height of split $H_2$	height of bottom $H_3$	Total height $H$
The original size of heavy rail		44.0211	105.6507	26.3250	175.9967
Cooling after heavy rail dimensions (mm)	950°C	43.9810	105.5599	26.3026	175.8435
	900°C	43.9840	105.5665	26.3042	175.8546
	870°C	43.9866	105.5723	26.3056	175.8646
	850°C	43.9869	105.5728	26.3058	175.8654
Height contraction after cooling (mm)	950°C	0.0401	0.0907	0.0224	0.1532
	900°C	0.0371	0.0842	0.0208	0.1421
	870°C	0.0345	0.0784	0.0193	0.1322
	850°C	0.0342	0.0779	0.0192	0.1313
Height contraction rate after cooling	950°C	0.9109‰	0.8589‰	0.8491‰	0.8704‰
	900°C	0.8248‰	0.7971‰	0.7886‰	0.8072‰
	870°C	0.7826‰	0.7418‰	0.7343‰	0.7509‰
	850°C	0.7769‰	0.7371‰	0.7299‰	0.7460‰

Table 4 Different initial temperatures cooled rail width variation

Measure location	Initial temperature	width of railhead top $B_1$	width of railhead middle $B_2$	width of railhead bottom $B_3$	width of split $B_4$	width of bottom $B_5$
Heavy rail to the original size(mm)		60.1480	70.2914	73	16.5461	150
Cooling after heavy rail dimensions (mm)	950°C	60.0934	70.2277	72.9338	16.5320	149.8770
	900°C	60.0975	70.2324	72.9387	16.5330	149.8856
	870°C	60.1011	70.2366	72.9431	16.5339	149.8933
	850°C	60.1014	70.2370	72.9435	16.5340	149.8939
Width contraction after cooling (mm)	950°C	0.0546	0.0637	0.0662	0.0141	0.1230
	900°C	0.0505	0.0590	0.0613	0.0131	0.1144
	870°C	0.0469	0.0548	0.0569	0.0122	0.1066
	850°C	0.0466	0.0544	0.0565	0.0121	0.1061
Width contraction after cooling	950°C	0.9070‰	0.9064‰	0.9075‰	0.8495‰	0.8197‰
	900°C	0.8394‰	0.8388‰	0.8398‰	0.7888‰	0.7626‰
	870°C	0.7795‰	0.7790‰	0.7799‰	0.7343‰	0.7110‰
	850°C	0.7740‰	0.7735‰	0.7744‰	0.7298‰	0.7071‰

### Summary

1. With the increasing of initial temperature, the bending curvature radius of cold rail is reducing, its curvature increased, and the cooled rail bending reduced through appropriate reducing the initial cooling temperature.
2. After cooling process, the height of rail-head's contraction rate is the most, the height of split's the second, and the height of bottom's the minimum. As the initial temperature increases before cooling, the contraction and contraction rates along cooled rail height direction increased with it, but the increment is little.
3. After cooling, the top of rail head width  $B_1$ , the middle width  $B_2$  and the lower part of rail head width  $B_3$  contraction is the maximum, and basically the same, the contraction of rail split width  $B_4$  is less than that, the contraction of bottom width  $B_5$  is the minimum. As the initial temperature before the cooling increased, the width dimension contraction and contraction rate of cooled rail increased with it.

### Acknowledgement

Supported by National Science Foundation of China, ID5107488.

### References

- [1] Hua Guo, Deng Yong. Simulation analysis of rail's bending formation during cooling process. 2006 Conference on theory and technology of plastic processing in China, 2006, Qingdao.
- [2] Li Ge, Jia Baohua, Jiang Xu. Finite element analysis of bending deformation in the cooling process before straightened of hundred-metre U75V heavy rail. Special steel, 2010, 6, 31(3): 14-16.
- [3] J Basu, S L Srimani, D S Gupta. Rail behavior during cooling after hot rolling. The Journal of Strain Analysis for Engineering Design. 2004, Vol.39, No. 1: p.15-24.
- [4] Xu Zhuyao. Thermodynamics of metallic material. Beijing: Science press, 1981.7.
- [5] Zhou Jianhua, Lin Gang, Wu Di, Zhao Xianming. Finite element simulation and analysis of the temperature field during the cooling of 60kg/m heavy rail. Journal of iron and steel research.2007, Vol.19, No.11: 29-32.